

COURSE OUTLINE
FORS 340 - FOREST PRODUCTS MANUFACTURING
Autumn Semester 2017
2 Credits

Course and Instructor Information

Instructor: Ed Burke
Office: Stone Hall 105
Phone: 243-5157
Course Schedule: Lecture Tuesday, 18:00.to 20:50, FORESTRY 301
Laboratory Wednesday and Thursday, 14:00 to 17:00, Meet in Stone Hall 102 (Wood Lab)
Special Lab Tour: Date to be announced: All-Day Monday or Friday lab trip to see lumber production as well as treated wood products.
Suggested/ Optional Text: *Forest Products and Wood Science* by Bowyer, Shmulsky and Haygreen, 5th. Edition, Blackwell Publishing, Ames, Iowa. 2007.

Field trips and exercises showing different forest product manufacturing will be conducted during laboratory periods, throughout the semester. Some laboratory exercises will also be held in the classroom and in the Wood Science Laboratory, Journalism 102. Specific details of these laboratory sessions will be announced in class.

Week 1 Introduction; Wood Structure and Fundamental Properties.

We begin with discussions of anatomical directions and planes in the tree and xylem, as well as covering the fundamental wood structure and properties. We will also discuss and work problems in determining wood density, moisture content, shrinking and swelling. **Laboratory;** Students will determine wood moisture content, density, specific gravity and total shrinkage in the longitudinal, radial, tangential directions, as well as volumetric shrinkage. Each student will be responsible for producing a laboratory write-up with results of their investigation. Students will be assigned times to report to Wood Lab to make their measurements.

Week 2 Lumber Production;

The report of first laboratory's exercise is due at beginning of lecture. Lumber manufacturing and recovery factor, between and within board variation, various growth and manufacturing characteristics and fundamental lumber grading will be covered. **Laboratory;** Meet outside the Wood Lab's roll- up door no later than 14:00. Lumber milling exercise at Wood Science Laboratory's sawmills at Lubrecht Forest. Students will be shown and operate both circular and band headsaw mills. NO SHORTS OR SANDALS!! Wear forestry field clothes, including work gloves, long pants, button shirts, boots.

Week 3 Veneer and Plywood;

Discussion focuses on the rotary and sliced veneer and plywood industry, including the types of adhesives used to bond these products. Other veneer products, such as Laminated Veneer Lumber will be introduced. Regular Laboratory; Teams of 2-3 students will select veneer plies, spread adhesive, layup a panel, press and trim their own plywood. Teams will be scheduled for lab instruction sessions and panel layup operations. NOTE:A rough draft of the report of the Lubrecht lumber production laboratory (primarily floor plan and flow charts of the two mills and the verbal write-up of the mill's History, employment, products, markets, process, costs and future outlook is due at the beginning of lecture.

Week 4 Examination #1; No laboratory this week

2-hour written exam w. moisture content, shrinking and swelling, as well as lumber and plywood manufacturing flow diagrams, equipment identification and explanations, definitions, flow diagrams to draw. **Laboratory:** No laboratory activity this week.

Week 5 Composites and Engineered Structural Panels and Beams;

Manufacturing processes involved in manufacture of Particleboard, Oriented Strand Board and Hardboard. **Laboratory;** Tour of Roseburg Forest Products particleboard plant in Missoula. NO SHORTS OR SANDALS!! Wear forestry field clothes, including long pants, button shirts, boots.

Week 6 Mechanical Properties of Wood;

Discussion of the mechanical properties of solid wood and the physics and engineering used in their evaluation. **Laboratory;** Mechanical Properties Exercise. Groups will conduct static bending testing of full-size lumber using the methods of ASTM Standard D-193. You will calculate moisture content, specific gravity, Modulus of Elasticity and Modulus of Rupture. Groups of 3-4 students will each prepare, test and summarize group testing results from a static bending test-to-failure.

Week 7 Paper and Interesting Specialty Products;

Laboratory; this week's laboratory to be announced.

Week 8 Lecture Final Examination;

A 2-Hour lecture final covering entire course, but 75% of the questions will pertain to material covered since Examination #1, including particleboard, fiberboard and other engineered panels, paper and, finally, mechanical properties. **Laboratory Final Examination;** 1-hour laboratory final, immediately following lecture final. Examination will cover the identification of specimens of wood products as well as various raw materials, finished products, tools and equipment used in the of the products covered during the semester. Some simple mathematical computations (moisture content, specific gravity etc.) similar to those on the lecture final and Examination #1 may also be present on the Lab Final.

Special All-Day Laboratory Trip;

Special, day-long trip to a mill complex(es) in w. Montana to see lumber, plywood and medium density fiberboard plants. Leave Forestry School Parking Lot at 07:30 return at 18:30. Bring sack lunch and snacks. NO SHORTS OR SANDALS!! Wear forestry field clothes, including long pants, button shirts, boots. Bring civilian clothes for the ride home, if desired, but have your field clothes on when we leave so we can get out of the vans and go right into a tour.

Notice: Burke may have to travel and work out-of-state one week during this course. If so, the lecture and lab schedule will be pushed back accordingly.

Laboratory sessions for the course will consist of both exercises held inside the Wood Science Laboratory as well as field trips to the Lubrecht Forest and Roseburg Lumber Co.'s Missoula particleboard plant.

- **No sandals or shorts are permitted on field trips.**
- **Hard hats, eye & hearing protection and safety vests will be furnished and WORN at all times when on plant grounds and buildings.**
- **Field boots and gloves, in addition to the other Personal Protective Equipment, are strongly advised, especially for the Lubrecht field trip and the mechanical testing exercises.**

Final reports on laboratory tours due at beginning of period. Final report collection will include the three

Student Conduct Code

All students must practice academic honesty. Academic misconduct is subject to an academic penalty by the course instructor and/or a disciplinary sanction by the University. All students need to be familiar with the [Student Conduct Code](http://life.umt.edu/vpsa/student_conduct.php). http://life.umt.edu/vpsa/student_conduct.php.

Important Dates Restricting Opportunities to Drop a Course:

DATES	DESCRIPTION	TIMELINE
To 15 th instructional day	Students can drop classes on CyberBear with refund	13 September is the last day for unrestricted drops
16 th to 45 th instructional day	Drop requires form with instructor and advisor signature, a \$10 fee from registrar's office, student will receive a 'W' on transcript, no refund.	14 September through 30 October
Beginning 46 th instructional day	Students are only allowed to drop a class under very limited and unusual circumstances. Not doing well in the class, deciding you are concerned about how the class grade might affect your GPA, deciding you did not want to take the class after all, and similar reasons do not qualify as "very limited and unusual circumstances". If you want to drop the class for these less serious sorts of reasons, make sure you do so by the end of the 45 th instructional day of the semester.	2 November

Class Attendance Policy

- Students who are registered for a course but do not attend the first two class meetings may be required to drop this course. This rule allows for early identification of class vacancies to permit other students to add classes. Students not allowed to remain must complete a drop form or drop the course on the Internet (<http://cyberbear.umt.edu>).
- Students are expected to attend all class meetings and complete all assignments for this course. Student may excused for brief and occasional absences for reasons of illness, injury, family emergency, religious observance or participation in a University sponsored activity. (University sponsored activities include for example, field trips, ASUM service, music or drama performances, and intercollegiate athletics.) Students shall be excused for military service or mandatory public service.
- Students incurring an excused absence will be allowed to make up missed work when done in a manner consistent with the educational goals of this course.
- Students expecting to incur excused absences should consult with the instructor early in the term to be sure that they understand the absence policies for this course.

FORS 340 - TIMBER HARVESTING AND FOREST PRODUCTS

Laboratory #1, Exercise #1

Determining a Sample's Moisture Content and Specific Gravity

This exercise is designed to teach the methods used in determining moisture content, size and shape after drying and green lumber target size

Step 1. Measurement of Mass/Weight

- Determine and record the current (green) masses of samples with the laboratory balance.

Step 2. Measurement of Volume

- Set beaker of water on balance and tare balance to 0.0
- Affix block to end of knife blade with rubber stopper on handle
- Immerse block deep enough in water to cover block, placing rubber stopper in clamp on vertical support.
- Immediately read value of mass of displaced water and record
- Remove block from knife tip and repeat for second sample block
- Record the values for green volume in Measurements Table

Step 3. Drying Sample Blocks

- Place identified blocks in oven set at 105C.
- Following removal of all moisture (block loses no more mass), the blocks are ready for re- measuring

Step 4. Obtain OD Mass/Weight and Volume

- Remove OD blocks from oven and immediately weigh on balance to obtain OD mass/weight
- Record OD weight of each block in Measurements Table
- Determine OD volume using methods of Step 2. and record values in Measurements Table

Step 5. Determination of Wood Moisture Content.

- Moisture Content (%) = $\frac{(\text{Green wt.} - \text{Oven Dry wt.})}{\text{Oven Dry wt.}} \times 100$

Step 6. Determination of Specific Gravity

- Specific Gravity is determined by computing the mass and volume of a block (green, oven dry or in-service conditions). Most handbooks use Green Volume and Oven Dry weight to compute the specific gravity using the following formula: $SG = \frac{\text{Density of Wood}}{\text{Density of Water}}$. The density of wood is computed by determining the wood's weight and volume. Therefore, knowing that the density of water in the metric system is 1 gm. / 1cc (ml) or 62.4 lbs./ft³, the specific gravity is computed for the weight and volume using the combination of wt. / volume.
- Determine Specific Gravity using Green Volume and Green wt.
- Determine Specific Gravity using Green Volume and OD wt.
- Determine Specific Gravity using OD Volume and OD wt.

Why are these values different? What is the most useful value to use to estimate the effect of moisture content and specific gravity on a structural member?

WARNING!

Always make immersion volume measurement AFTER making mass measurements

1. Make green and dry mass (weight) measurements for both Sample A and Sample B. and record in Mass and Volume Table.
2. Make green and dry volume measurements of A and B by immersion and record in Mass and Volume Table.

Mass and Volume Measurements Table

Values	Immersion Volume (measure after measuring mass) (cc)		Block Weight/Mass (measure first before measuring immersion volume) (grams)	
	Sample Block "A"	Sample Block "B"	Sample Block "A"	Sample Block "B"
Value @ Test (green)				
Value when Oven Dry				

3. Using formula for determining Moisture Content, compute and record the Moisture Content of Sample A and Sample B. Complete table by computing the means of these values

Moisture Content Computation Table

Sample Block "A"	Sample Block "B"	Mean

4. Using formulae in Specific Gravity Table's first column, compute and record the Specific Gravity for Sample A and Sample B. You will compute SG for test (green) wt./green volume, test wt./OD volume and, finally, OD wt./OD vol. Complete table by computing the means of these three values

Specific Gravity Computation Table

Mean Specific Gravity Formula	Result for Sample Block "A"	Result for Sample Block "B"	Mean
Wt. @ test./ vol. @ test			
Wt. @ test /OD			
OD wt./OD vol.			

FORS 340

Example of Determining the Finished Size of a Lumber Specimen Following Drying

This exercise is designed to teach the methods used in determining size and shape of solid wood after drying.

How to Determination of Shrinkage

Given:

Specimen is a green, quarter-sawn interior north Douglas-fir “2 x 12, with as-sawn dimensions of 12.000” wide x 2.000” thick x 96.000” long. Assume the FSP = 30%, the starting MC is > 60%, and the desired ending MC = 19%

- Determine the species of the specimen
- Determine the ring orientation (wide face/narrow face; radial and tangential directions)
- Determine the amount of shrinkage expected based on Wood Handbook tabulated values for each direction and face on the sample
- Determine or set beginning and ending moisture contents, and Fiber Saturation Point
- Assume linear relationships for all 4 shrinkage values (fiber saturation point to 0% MC); Longitudinal, Radial, Tangential and Volumetric
- Calculate % shrinkage for each anatomical direction in the specimen using the tabulated values for the species’ shrinkage and the assumed/given fiber saturation point, beginning and ending moisture content
- Wood Handbook equation 3-4
$$S_m = S_o ((FSP - M)/FSP)$$

where:

S_m = Shrinkage (%) from the green condition to moisture content M (<30%) M = desired ending moisture content (<30%)

S_o = total % shrinkage (radial, tangential or volumetric)

GENERAL SOLUTION for Part 1:

Using Wood Handbook values for shrinkage of the species of interest, Douglas- fir, the assumed Fiber Saturation Point, and the preselected final moisture content, determine the estimated loss of width and thickness, in inches, and subtract that from the green dimensions.

Specific solution:



First step; obtain shrinkage data for interior north Douglas-fir from Table 3-5 of the Wood Handbook *Radial = 3.8%, Tangential = 6.9%, Volumetric (not needed in this problem) =10.7%*. Longitudinal shrinkage (not needed in this problem) is often insignificant (0.1-0.2%) in normal, non-juvenile wood. You can disregard longitudinal shrinkage in most cases.

Second step; compute shrinkage in width and thickness, based on the beginning dimensions, the assumed FSP, the stated ending MC and the handbook values of radial and tangential shrinkage applied to the width and thickness properly.

- A. Determine the % width shrinkage when dried to new moisture content: $S_m(\text{radial}) = 3.8\% \left(\frac{30\% - 19\%}{30\%} \right)$
 $= 3.8\% (0.3666)$
 $= \underline{1.39\% \text{ loss of width due to shrinkage}}$
- B. Determine the % thickness shrinkage when dried to new moisture content: $S_m(\text{tangential}) = 6.9\% \left(\frac{30\% - 19\%}{30\%} \right)$
 $= 6.9\% (0.3666)$
 $= \underline{2.53\% \text{ loss of thickness due to shrinkage}}$

Third step; compute the dry cross-section dimensions of dried lumber specimen

- A. Determine the dry width @ :
 Width @ 19% = green width – (green width x .0139)
 $= \text{green width} \times (1 - .0139)$
 $= 12.000 \times 0.9861$
 $= \underline{11.833''}$
- B. Determine the dry thickness:
 Thickness @ 19% = green thickness – (green thickness x .0253)
 $= \text{green thickness} \times (1 - .0253)$
 $= 2.000 \times 0.9747$
 $= \underline{1.949''}$

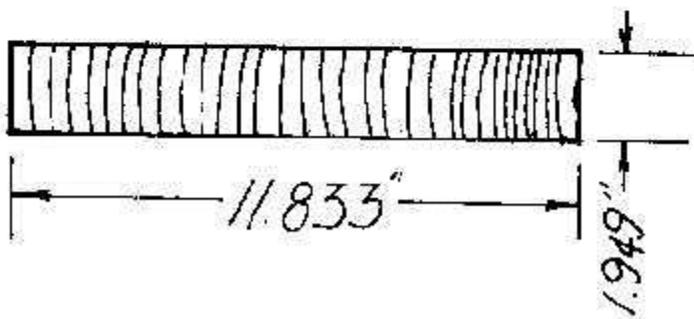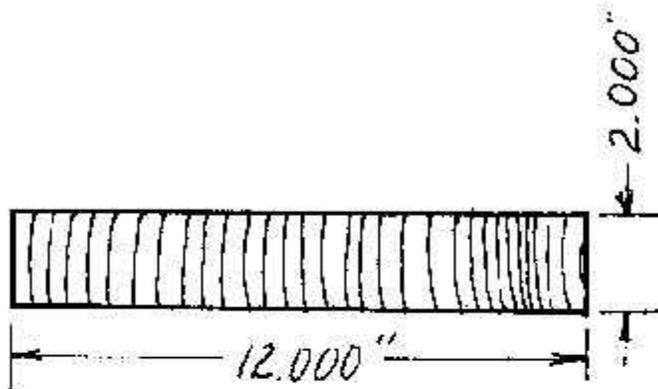

FORS 340

Moisture Content Determination and Lumber Shrinkage Problem #1

- I. Given a sample of sample of a package of Douglas-fir/western larch lumber that has a green mass of 31.26 grams while displacing 62.52 cc, and has an oven-dry mass of 25.44 grams and OD volume of 58.6 cc, what is its beginning moisture content (%) and density (gms. / cc), and what is its density at OD conditions (gms/cc & lbs. / ft³? The density of water is equal to 1 gm/cc or 62.4 lbs./ft³. If specific gravity, G, is equal to the density of wood over the density of water, what is the specific gravity of the lumber specimen at the time of sampling (green condition) and at oven dry (0%)?
- II. Given the preceding sampling results for moisture content, density and specific gravity, estimate the weight of 1,000 bd. Ft. of 2"x6"x10' Douglas-fir/western larch at 22.88% mc. (Hint: Specific gravity of a specimen multiplied times the density of water (lbs./ft³) will yield the average density of the lumber in lbs./ft.³)

Solution to Problem #1, Part I:

1. Compute the original moisture content of the sample using the following formula:

$$\begin{aligned} \text{MC (\%)} &= ((\text{Green wt.} - \text{OD wt.}) / \text{OD wt.}) \times 100 \\ &= ((31.26 \text{ gms.} - 25.44 \text{ gms.}) / 25.44 \text{ gms.}) \times 100 \end{aligned}$$

$$\text{MC}_{\text{original}} = \underline{\underline{22.88\%}}$$

2. Compute the metric density of the sample at green condition using the following method:

$$\begin{aligned} \text{Density} &= \text{Mass green} / \text{Volume green} \\ &= 31.26 \text{ gms.} / 62.52 \text{ cc.} \end{aligned}$$

$$\text{Density}_{\text{green}} = \underline{\underline{.50 \text{ gms/cc}}}$$

3. Compute the metric density of the sample at OD condition using the same method but using OD mass and volume:

$$\begin{aligned} \text{Density} &= \text{Mass @ OD} / \text{Volume @ OD} \\ &= 25.44 \text{ gms.} / 58.6 \text{ cc.} \end{aligned}$$

$$\text{Density}_{\text{OD}} = \underline{\underline{.43 \text{ gms/cc}}}$$

4. Compute the specific gravities using the following formula:

$$\begin{aligned} \text{Specific Gravity (G)} &= \text{Density of wood} / \text{Density of water} \\ G_{\text{green}} &= (.50 \text{ gms/cc}) / (1 \text{ gm. /cc}) \end{aligned}$$

$G_{\text{green}} = .50$ Note: G has no units. It is a ratio of densities.

$$G_{\text{dry}} = (.43 \text{ gms/cc}) / (1 \text{ gm/cc})$$

$G_{\text{dry}} = .43$

Solution to Problem #1, Part II:

1. Compute the density, in lbs./ft.³, of the lumber sample @ 22.88% MC.

$$\begin{aligned}\text{Density (lbs./ft}^3\text{) @ green condition} &= G_{\text{green}} \times \text{Density of Water} \\ &= .50 \times 62.4 \text{ lbs. /ft}^3\end{aligned}$$

$$\text{Density}_{\text{green}} = \mathbf{31.2 \text{ lbs. /ft.}^3}$$

2. Determine the actual volume of a finished 2 x 6 x 10' piece of lumber using standard dimensions:

If nominal thickness is 2", the actual thickness is 1.500"

If nominal width is 6", the actual width is 5.5"

If nominal length is 10', the actual length is 10' x 12"/lineal foot = 120.000"

$$\text{Volume}_{\text{actual}} = (\text{Actual Thickness (in.)} \times \text{Actual Width (in.)} \times \text{Actual Length (in.)}) / 1,728 \text{ in}^3/\text{ft}^3$$

remember that $1\text{ft.}^3 = 12'' \times 12'' \times 12''$

$$1 \text{ ft.}^3 = 1,728 \text{ in.}^3$$

$$\text{Volume}_{\text{actual}} = (1.5 \times 5.5 \times 120) / 1,728$$

$$\text{Volume}_{\text{actual}} = \mathbf{0.573 \text{ ft.}^3/\text{piece}}$$

3. Determine the nominal (nom.) board-foot volume of each piece of lumber (volume used for buying and selling:

$$\begin{aligned}\text{Volume}_{\text{nom}} &= (\text{nom. thickness (in.)} \times \text{nom. width (in.)} \times \text{nom. length (ft.)}) / 12 \\ &= (2'' \times 6'' \times 10') / 12\end{aligned}$$

$$\text{Volume}_{\text{nominal}} = \mathbf{10 \text{ bd. ft. / piece}}$$

4. Determine the actual weight of each piece of dry, finished lumber:

$$\begin{aligned}\text{Weight} &= \text{actual volume of each piece (ft}^3\text{)} \times \text{Density (lbs./ft}^3\text{)} \\ &= 0.573 \text{ ft}^3 \times 31.2 \text{ lbs./ft}^3\end{aligned}$$

$$\text{Weight} = \mathbf{17.88 \text{ lbs. / piece}}$$

5. Determine the number of pieces in the load

$$\begin{aligned}\# \text{ of pieces} &= \text{nominal volume of load} / \text{nominal volume of each piece} \\ &= 1,000 \text{ bd. Ft.} / 10 \text{ bd. Ft./piece}\end{aligned}$$

$$\# \text{ of Pieces} = \mathbf{100}$$

6. Determine the weight of the entire load;

$$\text{Total weight} = \text{weight of 1 piece} \times \# \text{ of pieces}$$

$$\text{Total weight} = 17.88 \text{ lbs. /pc.} \times 100 \text{ pcs.}$$

$$\text{Total load weight} = 1,788 \text{ lbs.}$$

$$\text{Total estimated weight of the load} = \mathbf{1,788 \text{ lbs.}}$$

Lumber Shrinkage, Weight and Cost Problem #2


- I. Calculate the approximate dry (15% MC) width and thickness ($\pm .001''$) of a green, quartersawn sawn (55% MC), redwood 2" x 10" x 16' whose actual rough green-sawn dimensions are 9.750" x 1.880" x 192.000" Be sure to draw the correct growth ring orientation in the rectangles on the answer sheet, and place the beginning and end dimensions in the places provided.

- II. Determine the approximate dry (10%MC) weight (lbs.) of one (1) piece of this lumber.

- III. Determine the cost of one (1) piece of this lumber
 - The Fiber Saturation Point (MC where shrinkage begins) is 30%.
 - The dry Target Moisture Content is 15%.
 - Total volumetric shrinkage = 9%,
 - Total tangential shrinkage = 5.5%
 - Total radial shrinkage = 3.1%
 - Total longitudinal shrinkage = .1%
 - Show your work below the diagrams in order to obtain credit.
 - Specific gravity of this lumber at 15% MC = .40
 - Cost of this lumber is \$975.00 / Mbf (thousand board feet)
 - Density of water = 1 gm./ 1cc or 62.4 lbs./ft.³

Solution to Problem #2, Part I:

1. First, draw in the growth rings in the correct orientation in both rectangles. Then fill in the beginning rough green dimensions in the left diagram.

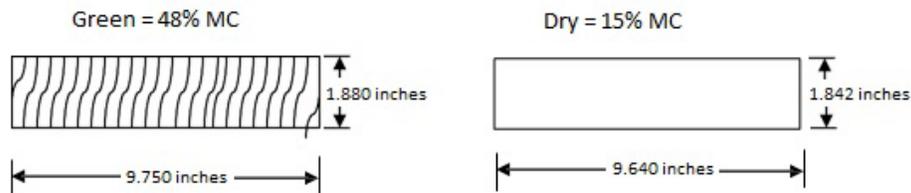

2. Determine dry dimensions of lumber
 Dry Size = Green Size - [Green Size x (((FSP-MC)/FSP) x Total Shrinkage)]

$$\begin{aligned} \text{Width} = \text{Radial} &= 9.750 - [9.750 \times (((30-19)/30) \times .031) \\ &= 9.750 - 0.110 \end{aligned}$$

Width = 9.640"

$$\begin{aligned} \text{Thickness} = \text{Tangential} &= 1.880 - [1.880 \times (((30-19)/30) \times .055)] \\ &= 1.880 - 0.038 \end{aligned}$$

Thickness = 1.842"

3. Make cost calculations using nominal size

$$\begin{aligned}\text{Cost/piece} &= \text{Bd.ft./piece} \times \text{cost/Bd. Ft.} \\ &= ((2 \times 10 \times 16)/12) \times (\$975/\text{Mbf} / 1000 \text{ Bd.ft.} / \text{MBF}) \\ &= 26.66 \text{ Bd. Ft.} / \text{piece} \times \$975 / \text{Bd. ft.}\end{aligned}$$

Cost/piece = \$26.00

4. Make weight calculations using actual size

$$\begin{aligned}\text{Weight/ piece} &= \text{Wood Density} \times \text{Volume /piece} \\ \text{Wood Density} &= \text{Wood Specific Gravity}_{\text{dry}} \times \text{Density of Water}\end{aligned}$$

$$\text{Wood Density} = .40 \times 62.4 \text{ lbs.} / \text{ft.}^3$$

5. Determine wood density (lbs./ft³) using given specific gravity

$$\begin{aligned}\text{Wood Density} &= \text{Specific Gravity}_{\text{MC}\%} \times \text{Density of Water} \\ &= 0.40 \times 62.4 \text{ lbs./ft.}^3\end{aligned}$$

$$\text{Wood Density} = 24.96 = 25 \text{ lbs.} / \text{ft.}^3$$

6. Determine the Volume / piece

$$\begin{aligned}\text{Volume / piece} &= [\text{Width (in.)} \times \text{Thickness (in.)} \times \text{Length (in.)}] / 1728 \text{ in.}^3 / \text{ft.}^3 \\ &= 11.362 \times 1.839'' \times (14' \times 12) / 1728\end{aligned}$$

$$\text{Volume / piece} = 2.031 \text{ ft.}^3 / \text{piece}$$

$$\text{Weight/ piece} = 25 \text{ lbs./ft}^3 \times 2.031 \text{ ft}^3 / \text{piece}$$

Weight/piece = 50.78 lbs.
